

Solubility and superconductivity in $\text{RE}(\text{Ba}_{2-x}\text{RE}_x)\text{Cu}_3\text{O}_{7+\delta}$ systems (RE=Nd, Sm, Eu, Gd, Dy)

This article has been downloaded from IOPscience. Please scroll down to see the full text article.

1987 J. Phys. C: Solid State Phys. 20 L935

(<http://iopscience.iop.org/0022-3719/20/34/001>)

View [the table of contents for this issue](#), or go to the [journal homepage](#) for more

Download details:

IP Address: 132.239.69.137

The article was downloaded on 02/02/2012 at 00:51

Please note that [terms and conditions apply](#).

LETTER TO THE EDITOR

Solubility and superconductivity in RE(Ba_{2-x}RE_x)Cu₃O_{7+δ} systems (RE = Nd, Sm, Eu, Gd, Dy)

K Zhang[†], B Dabrowski, C U Segre[†], D G Hinks, Ivan K Schuller[‡],
J D Jorgensen and M Slaski

Division of Materials Science, Argonne National Laboratory, Argonne, IL 60439, USA

Received 19 October 1987

Abstract. Solid solutions of RE(Ba_{2-x}RE_x)Cu₃O_{7+δ} (RE = Nd, Sm, Eu, Gd, Dy) for $x = 0$ to $x = 0.5$ have been investigated. X-ray and resistivity measurements show that there exists a solid solution region, through which the structure changes from orthorhombic to tetragonal and the superconducting properties are depressed. The solubility limits depend strongly on the size of the rare-earth ion, with the smallest (Dy) showing no appreciable solubility. The superconducting transition temperature versus x for all of the rare-earth-ion substitutions falls on a universal curve, indicating that the Ba sites are extremely ionic and magnetically isolated.

Shortly after the discovery and isolation of the 90 K superconductor, YBa₂Cu₃O_{7-δ} [1–13], several papers appeared in which the Y was fully substituted by most of the rare-earth elements. Unlike previously studied superconducting materials, the presence of magnetic ions was not found to significantly alter the superconducting transition temperature, T_c [14–16]. Mössbauer studies on GdBa₂Cu₃O_{7-δ} showed that the rare-earth site could be considered strongly ionic and magnetically isolated from the rest of the crystal structure [17]. This is further proven by the results showing that the Néel temperature for the Gd sublattice in both orthorhombic and tetragonal structures is the same [18]. Among the trivalent rare earths, La was found to be the most difficult to substitute for Y, generally resulting in multi-phase samples and lower values of T_c [12]. Subsequently, it was discovered that La was in fact partially substituting for Ba, giving a solid solution of the form La(Ba_{2-x}La_x)Cu₃O_{7+δ} with a range $0.25 \leq x \leq 0.5$ [19, 20].

The present work was motivated by the question of whether other large rare-earth ions could be substituted for Ba, effecting changes in T_c . Our results indicate that the ability of a rare-earth ion to substitute onto the Ba site depends only on its size and that such substitutions of a 3⁺ (RE) ion for a 2⁺ (Ba) ion result in changes in the electronic and structural properties of the compound, independent of the particular rare-earth ion.

Between five and seven samples in the series RE(Ba_{2-x}RE_x)Cu₃O_{7+δ} were synthesised for each of the rare earths, Nd, Sm, Eu, Gd and Dy. The samples were prepared by mixing and grinding RE₂O₃, BaCO₃ and CuO powders in the correct metal stoichiometries and firing at 975 °C under flowing oxygen. All the samples were then reground and refired

[†] Permanent address: Department of Physics, Illinois Institute of Technology, Chicago, IL 60616, USA.

[‡] Also at Physics Department, University of California, San Diego, La Jolla, CA 92093, USA.

several times in order to improve homogeneity. A final annealing at 500 °C in flowing O₂ followed by furnace cooling to room temperature was important in obtaining the superconducting samples. X-ray diffraction data were obtained with a GE-XRD5 diffractometer using Cu K α radiation with wavelength $\lambda = 1.5418 \text{ \AA}$. Resistivities as a function of temperature were obtained in a closed-cycle refrigerator by the standard four-probe technique using Si diode thermometry traceable to NBS standards and accurate to about 0.5 K over the measured temperature range.

It should be noted that both solid solubility limits and superconducting transition temperatures presented here are characteristic of the preparation conditions employed in this study. We have frequently observed noticeable variation of T_c as a function of x even for minor changes in firing temperature, cooling rate and annealing temperature. Since no systematic study was performed to optimise the firing procedure for each rare earth separately, we consistently used one firing scheme for all rare earths. Under these conditions, it was somewhat difficult to obtain good superconducting samples for Nd, Sm and, in particular, La, which was the subject of our previous study [20].

Careful x-ray diffraction data have been taken for all five series in order to determine the solubility boundaries for the various rare earths. Figure 1 shows x-ray data for four representative Nd-substituted samples ($x = 0, 0.1, 0.2, 0.5$). It can be seen that the stoichiometric NdBa₂Cu₃O_{7- δ} superconducting phase does not form under our prep-

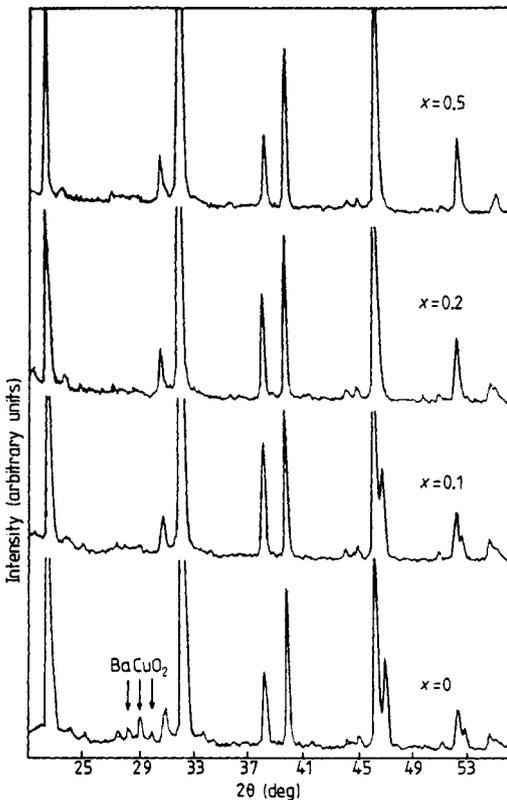


Figure 1. Powder x-ray diffraction data for four samples in the Nd(Ba_{2-x}Nd_x)Cu₃O_{7+ δ} system. The presence of BaCuO₂ in the $x = 0$ sample is indicated by characteristic peaks near $2\theta = 29^\circ$.

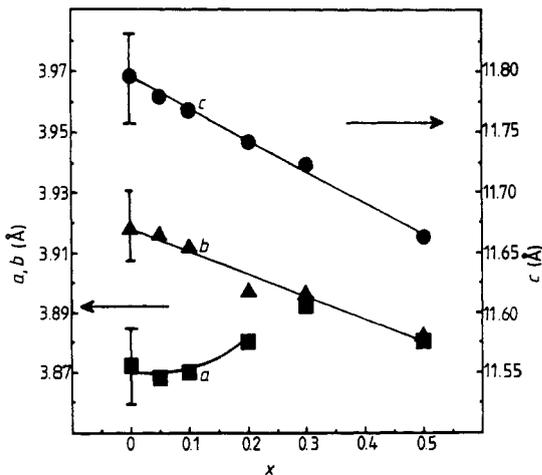


Figure 2. Orthorhombic lattice parameters *a* (■), *b* (▲) and *c* (●) for the Nd(Ba_{2-x}Nd_x)Cu₃O_{7+δ} system as a function of *x*. The error bars for the *x* = 0 data are representative of the error in measurement over the entire series. The lines and curve are drawn as a guide to the eye.

aration conditions, since the *x* = 0 sample contains a small amount of BaCuO₂ besides the main 1 : 2 : 3 phase. Thus, the Nd is substituting on both Y and Ba sites, just as was found in the La system [20]. As *x* is increased, the characteristic orthorhombic splitting of the (020), (200) and (006) reflections at $2\theta \approx 47^\circ$ becomes smaller and vanishes at *x* = 0.2 within the resolution of the diffractometer. The lattice parameters for the Nd series are shown in figure 2 as a function of *x*. These data were obtained by a least-squares fit

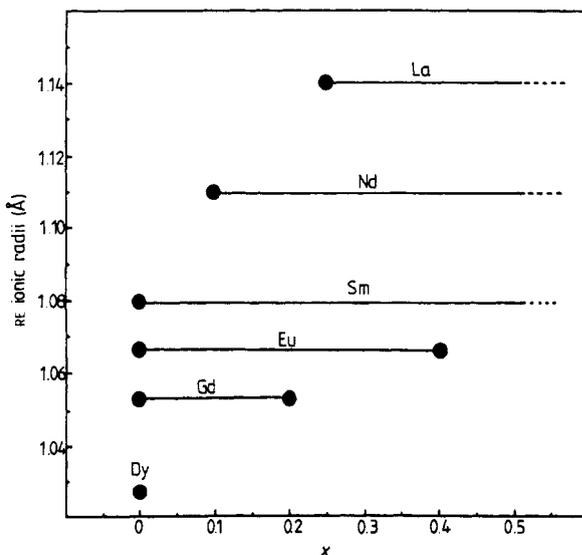


Figure 3. Solid solubility regions for the RE(Ba_{2-x}RE_x)Cu₃O_{7+δ} systems with RE = La, Nd, Sm, Eu, Gd and Dy. The full lines indicate the region in which a single phase is observed, while the broken lines indicate the possible extension of the single phase into regions not studied.

of the peak positions from the x-ray scans with an orthorhombic cell across the entire range ($0 \leq x \leq 0.5$). As x is increased, the b and c axes decrease monotonically, while the a axis increases until it merges with the b axis at $x \approx 0.2$. This collapse to an apparently tetragonal structure is a common feature in all of the series investigated here. It should be noted that in our previous neutron diffraction study of the $\text{La}(\text{Ba}_{2-x}\text{La}_x)\text{Cu}_3\text{O}_{7+\delta}$ system, there was evidence for a slight orthorhombic distortion even when the lattice constants had collapsed [20].

Figure 3 presents the solid solution region for La [20] and the five systems reported here as a function of rare-earth ionic radius. For the larger ions (La, Nd, Sm) the single-phase region extends all the way to $x = 0.5$. Values of $x > 0.5$ have not been tried, but may indeed exist for these ions. For both La and Nd, the solid solution limits do not extend to the stoichiometric 1:2:3 composition. As the rare-earth ion becomes smaller, the 1:2:3 compound is easily obtained and the maximum value of x for which there still exists a single phase becomes smaller until the solubility region collapses to a single point for Dy. Because Y is slightly smaller than Dy, we expect virtually no solubility region to exist and we have indeed confirmed this experimentally.

Figure 4 shows the superconducting transition temperatures as a function of x for all five systems investigated as well as La [20]. The error bars indicate the 90% and 10% points of the resistive transition. It is evident that for those rare-earth ions that can substitute onto the Ba site, the T_c decreases as a function of x along a more-or-less universal curve. The Dy system, in which we observed no solid solubility by x-ray diffraction, shows a distinctly different curve, with T_c remaining constant for all the samples, indicating the presence of only the stoichiometric 1:2:3 compound with $\text{Dy}_2\text{BaCuO}_5$ and CuO for those samples with $x > 0$. For Gd and La, the T_c data deviate at $x \geq 0.3$ and $x \leq 0.2$ respectively, consistent with the solubility limits found by x-ray

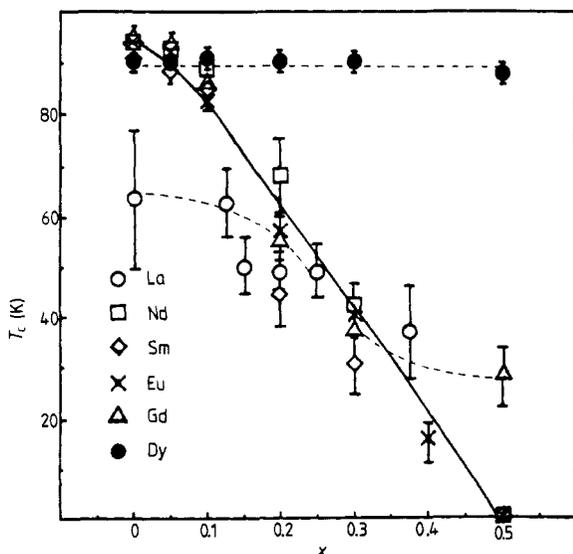


Figure 4. Superconducting transition temperature (as measured resistively) as a function of x for the systems $\text{RE}(\text{Ba}_{2-x}\text{RE}_x)\text{Cu}_3\text{O}_{7+\delta}$ with $\text{RE} = \text{La}, \text{Nd}, \text{Sm}, \text{Eu}, \text{Gd}$ and Dy . The error bars indicate the 90% and 10% points of the transition. Note the deviations from universal behaviour for La (○), Gd (△) and Dy (●), indicating the ends of their solubility regions.

and neutron diffraction. When the individual resistivities as functions of temperature are examined across a particular series, it is seen that as x increases, the sample behaves more and more like a semiconductor, an effect already reported for the $\text{La}(\text{Ba}_{2-x}\text{La}_x)\text{Cu}_3\text{O}_{7+\delta}$ system [19, 20].

The existence of a solid solubility regime for the $\text{RE}(\text{Ba}_{2-x}\text{RE}_x)\text{Cu}_3\text{O}_{7+\delta}$ systems can be easily explained by an ionic size argument. The lower bound of the solubility limit is controlled by whether the rare earth is small enough to substitute comfortably for the Y. The upper bound, on the other hand, extends to larger x only if the rare earth is large enough to fit in the Ba site. Thus, while it is difficult to obtain the stoichiometric 1:2:3 phase for the largest rare earths, La and Nd, it is entirely possible that the single-phase solubility limit for these ions and Sm could extend to compositions $x > 0.5$. This dependence on ionic size might also explain the difficulties in obtaining the stoichiometric 1:2:3 phase with Yb and Lu, the smallest of the rare-earth ions. In neutron diffraction studies on the La system [20], the presence of La on the Ba site disorders the one-dimensional Cu–O chains that are present in the parent $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$ compound. This disordering was found to correlate well with the depression of the superconducting transition temperature [20]. In these systems we expect that the same effect is occurring and neutron diffraction experiments on the Nd and Eu series, which have broader solubility regions, are currently under way to study this effect further. The remarkable feature is that there exists a universal curve for T_c as a function of x , showing that magnetic moments on the Ba site have no noticeable effect on the superconductivity. This, along with a similar result for the Y site [17], shows that both sites are extremely ionic and isolated from the conduction electrons that exist in the Cu–O layers.

The authors wish to thank R Marasas for collecting some of the x-ray data. This work was supported by the US Department of Energy BES–Materials Science under contract No W-31-109-ENG-38.

References

- [1] Wu M K, Ashburn J R, Torng C J, Hor P H, Meng R L, Gao L, Huang Z J, Wang Y Q and Chu C W 1987 *Phys. Rev. Lett.* **58** 908
- [2] Chu C W, Hor P H, Meng R L, Gao G, Huang Z J, Wang Y Q, Bechtold J, Campbell D, Wu M K, Ashburn J and Huang C Y 1987 *Phys. Rev. Lett.* **58** 405
- [3] Cava R J, Batlogg B, van Dover R B, Murphy D W, Sunshine S A, Siegrist T, Remeika J P, Reitman E A, Zahurah S and Espinosa G P 1987 *Phys. Rev. Lett.* **58** 1676
- [4] Hinks D G, Soderholm L, Capone D W II, Jorgensen J D, Schuller I K, Segre C U, Zhang K and Grace J D 1987 *Appl. Phys. Lett.* **50** 1688
- [5] LePage Y, McKinnon W R, Tarascon J M, Greene L H, Hull G W and Hwang D M 1987 *Phys. Rev. B* **35** 7245
- [6] Grant P M, Beyers R B, Engler E M, Lim G, Parkin S S P, Ramirez M L, Lee V Y, Nazzari A, Vasquez J E and Savoy R J 1987 *Phys. Rev. B* **35** 7242
- [7] Beno M A, Soderholm L, Capone D W II, Hinks D G, Jorgensen J D, Grace J D, Schuller I K, Segre C U and Zhang K 1987 *Appl. Phys. Lett.* **51** 57
- [8] Greedan J E, O'Reilly A and Stager C V 1987 *Phys. Rev. B* **35** 8770
- [9] Capponi J J, Chaillout C, Hewat A W, Lejay P, Marezio M, Nguyen N, Raveau B, Soubeyrou J L, Tholence J L and Tournier R 1987 *Europhys. Lett.* **3** 1301
- [10] David W I F, Harrison W T A, Gunn J M F, Moze O, Soper A K, Day P, Jorgensen J D, Beno M A, Capone D W, Hinks D G, Schuller I K, Soderholm L, Segre C U, Zhang K and Grace J D 1987 *Nature* **327** 310
- [11] Beech F, Miraglia S, Santoro A and Roth R S 1987 *Phys. Rev. B* **35** 8778

- [12] Katano S, Funahashi S, Hatano T, Matsushita A, Nakamura K, Matsumoto T and Ogawa K 1987 *Japan. J. Appl. Phys.* **26** L1046
- [13] Cox D E, Moodenbaugh A R, Hurst J J and Jones R H 1987 *J. Phys. Chem. Solids* at press
- [14] Hor P H, Meng R L, Wang Y Q, Gao L, Huang Z J, Bechtold J, Forster K and Chu C W 1987 *Phys. Rev. Lett.* **58** 1891
- [15] Tarascon J M, McKinnon W R, Greene L H, Hull G W and Vogel E M 1987 *Phys. Rev. B* **36** 226
- [16] Brown S E, Thompson J D, Willis J O, Aikin R M, Zirgniebl E, Smith J L, Fisk Z and Schwarz R B 1987 *Phys. Rev. B* **36** 2298
- [17] Alp E E, Soderholm L, Shenoy G K, Hinks D G, Capone D W II, Zhang K and Dunlap B D 1987 *Phys. Rev. Lett.* submitted
- [18] Dunlap B D, Slaski M, Sungalia Z, Hinks D G, Zhang K, Segre C U, Malik S K and Alp E E 1987 *Phys. Rev. B* at press
- [19] Mitzi D B, Marshall A F, Sun J Z, Webb D J, Beasley M R, Geballe T H and Kapitulnik A 1987 *Phys. Rev. B* at press
- [20] Segre C U, Dabrowski B, Hinks D G, Zhang K, Jorgensen J D, Beno M A and Schuller I K 1987 *Nature* **329** 227